

Development and test of new kinds of anti-vibration knitted hand protection

L.Kokas Palicska¹, F. Augusztinovicz², A. Szemeredy¹, L. Szucs¹

¹ *INNOVATEXT Textile Engineering and Testing Institute, Budapest, Hungary*

² *Laboratory of Acoustics and Studio Technologies, Budapest University of Technology and Economics, Hungary*
kokas@innovatext.hu

EXTENDED ABSTRACT

Key Words: personal protective gloves, vibration isolation, textile testing, cut resistance, safety workwear

1. INTRODUCTION

Anti-vibration gloves are an important sort of personal protective equipment (PPE), aimed at ensuring improved comfort in work with percussion drills, road-breakers and similar vibrating tools, and avoiding health impairment such as neurological changes, numbness and in a later phase reduced blood circulation, aka white finger disease. As any other protective workwear, apart from good vibration isolation paired with reasonable tractability, in particular cases anti-vibration gloves should also have appropriate resistance to cutting (sharp objects, knives) and fire too.

The degree of vibration reduction provided by gloves generally depends on the thickness and softness of the lining (resilient gel, foam or rubber-like material, or an array of air bladders), but also from the person in work [1]. On average, anti-vibration gloves must provide considerable protection against relatively high vibration frequencies (200 Hz and above), and might not, on average, increase vibration levels at lower frequencies. To protect against lower vibration frequencies the contact areas of the glove need to contain thicker resilient material. This may seriously limit dexterity and comfort and the gloves may therefore be unsafe to use, and unacceptable to employees.

2. EXPERIMENTAL

Research was carried out the develop suitable testing equipment, and to select and further develop appropriate materials and the applicable technologies to manufacture novel cut resistant anti-vibration gloves as prototypes for protection, safety. Theoretical works dealing with adoption of techniques and solutions of already existing materials and fibres were made, extended by a wide-range of experimental and validation activities [2].

Two special apparatuses were designed and built: to perform cutting tests under well controlled conditions according to the international standard ISO 13997, and a test setup for the measurement of vibration isolation materials according to the standard ISO 9052-1 as well as for the determination of the overall vibration isolation of gloves following ISO 10819.

2.1 Materials

Samples in three-layer sandwich form were fabricated by using various technologies, where the upper layer consisted of 100% Kevlar or 100% Dynetex knitted fabric, as inner layers different space fabrics or silicon were selected, and 100% cotton fabric as underlining. Thickness, space fabrics, surface structures were variables.



Figure 1. Knitted samples with special surface

2.2 Measurements

10 knitted fabric and 23 three-layers samples were investigated. Protection of these samples against mechanical hazards (cutting) and fire were tested, and also ergonomical characteristics was evaluated. A number of tests were performed to achieve optimum performance in terms of vibration isolation, safety and tractability. The selected knitted materials were tested in the first phase of the development to determine their elasticity parameters such as stiffness and internal damping as a function of vibration amplitude of various frequencies and static load [2].

2.3 Test of cut and heat resistance

“Coup Test” according to the EN 388 standard and the “TDM-100 Test” according to MSZ EN ISO 13997:2000 was performed to evaluate mechanical risks for hand protection. The “TDM-100” test was carried out on the testing device (Fig.2) developed by Hungarian partners for INNOVATEXT in the framework of the research. Test of heat resistance was performed according to MSZ EN 407:2004 .



Figure 2. Cut resistance testing device in the laboratory of INNOVATEXT

2.4 Test of vibration isolation

The evaluation of the three-layers samples were performed according the requirements of the standard [3]. The load was a 8 kg pressing plate, size 200×200×25,6 mm (Fig.3). The level of vibration damping was calculated from the frequency response function (FRF) obtained from accelerometers fixed on the base plate and the pressing plate. (Note that FRF values lower than 1 mean damping, while higher values than 1 represent amplification.)

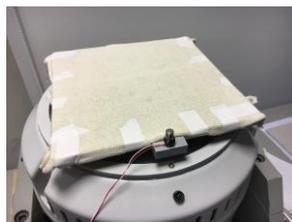


Figure 3. Measuring device for testing vibration isolation in the laboratory of BME

3. RESULTS AND CONCLUSION

Cut resistance of the knitted samples was 5 and 4 (from rate 1-5), according to the TDM-100: B, while all other physical performance factors or abrasion, tear and puncture resistance gave level 1. Samples including silicon and space fabric show significant anti-vibration characteristics in frequencies 10-200 Hz (Fig.4). The transmissibility value (y) decreases rapidly at frequency range of 50 – 130 Hz, the vibration was reduced by one to two orders of magnitude (corresponding to 20 to 40 dB damping). Further research and tests according to ISO 10819 should be continued to evaluate the prototype of gloves made from the selected fabrics with optimal performances.

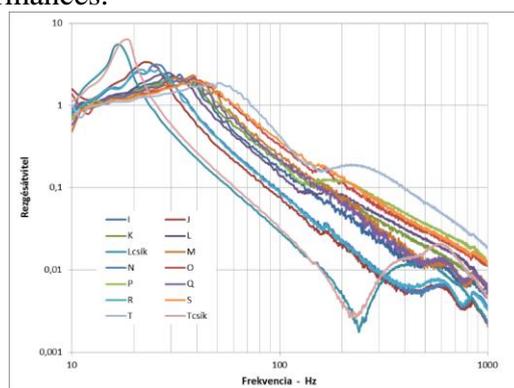


Figure 4. Vibration isolation of the measured samples

5. ACKNOWLEDGEMENT

The research was performed by the consortium consisting of a Hungarian glove manufacturer GLOVITA Zrt, a textile testing institute INNOVATEXT Zrt. and a university laboratory of BME, undertaking the complex task and supported by the EUREKA program in the framework of the ProTexSafe project ID 9918 *Functional Textiles for Vibration Protection, Safety and Well-being*. The authors would also like to thank Mr. F. Laufer and his team for their work in designing and producing special testing devices and for his scientific support during the research.

6. REFERENCES

1. Reynolds D.D., Angevine E.N. (1977): Hand-arm vibration, Part II: Vibration transmission characteristics of the hand and arm. *Journal of Sound and Vibration*, 51(2): 255-265.
2. PROTEXSAFE project, supported by EUREKA-16, Research report of BME No.47093/2017.
3. ISO 10846, Part 1 to Part 5. Acoustics and vibration - Laboratory measurement of vibro-acoustic transfer properties of resilient elements.

PROTEXSAFE
**DEVELOPMENT AND TEST OF NEW KINDS OF ANTI-VIBRATION
 KNITTED HAND PROTECTION**
 L.Kokas Palicska¹, F. Augusztinovicz², A. Szemeredy¹, L. Szucs¹
¹ INNOVATEX Textile Engineering and Testing Institute, Budapest, Hungary
² Laboratory of Acoustics and Audio Technologies, Budapest University of Technology and Economics, Hungary

Work with percussion drills, road-breakers, chainsaw and similar can leads to hand-arm vibration syndrome (HAVs). HAVs consists of disturbances the vibration in the circulation of the fingers (Vibration White Finger, VWF) and the peripheral nerves of the hands. (Fig.1)

- Anti-vibration gloves are aimed at
 - ensuring improved comfort
 - avoiding health impairment
 - ensuring resistance to cutting and fire
- Issues to be decided upon:
 - Composition
 - Fabrication technologies
 - Materials




Fig. 1. Vibration frequencies of chainsaw and the white finger disease

Experimental:

- Specimens in sandwich construction:
 - upper: 100% Kevlar or Dyntex
 - inner: space fabric or silicone gel
 - underlining: 100% cotton fabric
- Measurements and tests:
 - Vibration isolation measurements
 - Coup test
 - Heat resistance test

Measurements of resistance against thermal risks according to MSZ EN 407:2004

- Burning behaviour
- Contact heat
- Convective heat
- Radiant heat



Fig. 4. Heat resistance test according to MSZ EN 407:2004 the laboratory of INNOVATEX

Measurements of vibration isolation

- according to ISO 10846 : 2013, to proof the degree of protection against vibration at frequencies from 100 Hz up to 600 Hz.
- according to ISO 10819 : 2013 Measurement of the vibration transmissibility of gloves at the palm of the hand

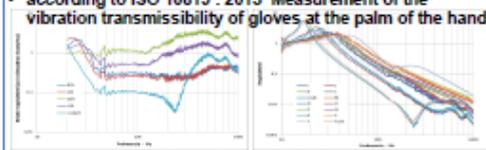


Fig. 2. Comparison of vibration damping



Fig. 3. Vibration isolation test in the laboratory of SME

Measurements of cut resistance according to the EN 388:2006 standard

- Cut resistance
- Abrasion resistance
- Tearing strength
- Puncture resistance

“TDM-100 Test” according to MSZ EN ISO 13997:2000



Fig. 4. Cut resistance test according to EN 388 and TDM 100 test in the laboratory of INNOVATEX

Results and discussion

New testing devices to measure hand-arm vibration and cut resistance according to the relevant standards were developed and validated. 23 knitted samples in 3-layers structure were produced and tested. Cut resistance of the tested knitted specimens acc. to EN 388 was 5 and 4 (from rating 1-5), and B according to the TDM-100, while all other physical performance factors like abrasion, tear and puncture resistance reached level 1. Samples including silicone gel and space fabric show significant anti-vibration characteristics in frequencies 10-200 Hz. The transmissibility value (γ) decreases rapidly at frequency range of 50 – 130 Hz, the vibration was reduced by one to two orders of magnitude (corresponding to 20 to 40 dB damping). Further research and tests according to ISO 10819 will be continued to evaluate the prototypes of gloves made from the selected fabrics with optimal performances.

Contact

EUREKA Research was supported by the EUREKA ProTexSafe project ID 9918 „Functional Textiles for Vibration Protection, Safety and Well-being”
 Innovation across borders

INNOVATEX Textile Testing and Engineering Institute Co.
 H-1159 Budapest, Gyömrői út 86.
 Dr. László Kokas Palicska
 E-mail: kokas@innovatex.hu
 www.innovatex.hu



AUTEX2019 – 19th World Textile Conference on Textiles at the Crossroads, 11-15 June 2019, Ghent, Belgium



PROJECT FINANCED FROM THE NRDI FUND
 MOMENTUM OF INNOVATION